



Dart Aerospace Ltd.
1270 Aberdeen St
Hawkesbury, ON
K6A 1K7
Canada

Tel (613) 632-5200

5

D350-748-141TRN
Job Sheet 174690



Part No: D350-748-141TRN

Job Qty: 1 ea

Part Name: Crosstube Turning Detail



Part Weight: 0 lbs

Status: Scheduled

Priority: Medium

Job Created: 3/20/18

Job Tracking No:

Due Date: 6/1/18

Created By: Marie Lajeunesse

Type: SOLD

Description:

Note: D350-748-141 REV H IPP Rev:A New Issue 08-03-06 DD verified by:ec IPP Rev B Removed polish 08.04.02
EC verified by : DD IPP Rev C Remove LPS-3 08.06.23 EC verified by DD IPP Rev C 11.02.24 as per dwg
rev.F DD verf: JLM

Ship Via:

Bill of Materials

Job Routing

Op No	Operation	Qty	Start Date	Due Date	Standard		Workcenter/Supplier		Sign-off
					Setup hrs	Run Hrs	Workcenter / Supplier	Lead Time	
90	Start up Operation	1 Ea		5/31/18	0.00	0.00	Start Up Crosstubes-1		M.D
100	Mori Seiki	1 pcs		5/31/18	7.06	2.81	Mori Seiki TL-40		M.D
110	QC	1 pcs		5/31/18	0.00	0.00	QC2-1		M.D
120	Mori Seiki	1 pcs		5/31/18	0.00	2.81	Mori Seiki TL-40		M.D
130	QC	1 pcs		5/31/18	0.00	0.00	QC2-1		M.D
140	QC	1 pcs		5/31/18	0.00	0.00	QC8		M.D
150	Crosstubes	1 pcs		6/1/18	0.00	0.97	Crosstubes-2		GP 18-05-30
160	QC	1 pcs		6/1/18	0.00	0.00	QC15 N/R		
170	Outsource	1 pcs		6/1/18	0.00	0.00	Outsource1		CC 18-6-5
180	Packaging	1 pcs		6/1/18	0.00	0.00	Packaging2		18-07-11
185	QC	1 pcs		6/1/18	0.00	0.00	QC6		18-07-13
190	Packaging	1 pcs		6/1/18	0.00	0.00	Packaging3-1		18-07-13
200	QC21-SA	1 Ea		6/1/18	0.00	0.00	QC21		18-07-13

Part Op 100 - 1-Fill tube with sand & install plugs on both ends as per Folio FA648 2-Turn first side as per Folio FA648 3- File
Descriptions: transition lines smooth. FOLIO REV: H DWG REV: H

120 - 1-Turn second side as per Folio FA648 2- File transition lines smooth. 3-Scribe Part & Batch as per Dwg D350-748-141 FOLIO REV: DWG REV:

130 - PERFORME ULTRASONIC MEASUREMENT

150 - 1-DRILL HOLES FOR HEAT TREAT USING DT9806(HOLES MUST BE ALIGNED ON SAME LINE ON BOTH CUFFS) 2-Grind machining marks

170 - Issue P/O: 040105 Heat Treat to min 180 KSI As per Dwg D350-748-141 (MIL-T-6736 OR AMS 2759-1C) ***Check for straighten and ensure parts are straight within 1/8" as per dwg *** Sand Blast tube after Heat Treat

Possible Supplier: Vac Aero Ensure Certificate of Conformity is attached and Metlab process spec form

190 - Identify and stock in kanban rack

Job BOM

Part / Item	Component Name	Quantity	Operation	Container
D6015-125	Crosstube Material	1 Ea (1 ea)	90-Start up Operation	

8128 725

Job Allocations

Operation	Component Part	Required	Inventory	Allocated
90-Start up Operation	D6015-125	1	0	0

Part Specifications

Specifications could not be found.

Plex 3/20/18 3:04 PM Dart.lajeunesse.marie



Container No: S069082



Part: D350-748-141TRN

Job No: 174690

Serial No/Batch: S069082

Revision: H

Inspector:

Dart Aerospace Ltd.
1270 Aberdeen Street
Newbury, ON K8A 1K7
CANADA
TEL: 1 813 632-8200
Email: sales@dartaero.com
www.dartaerospace.com

Date: 05/07/18


DART AEROSPACE LTD		Work Order: 177690
Description: Crosstube Assembly (AS350/355 High Fwd)		Part Number: D350-748-141
Inspection Dwg: D350-748-141 Rev: H		Page 1 of 2

FIRST ARTICLE INSPECTION CHECKLIST

Inspection Sheet	Drawing Dimension	Tolerance	Actual Dimension	Accept	Reject	Method of Inspection	Comments
SIDE A	2.240	+/-0.005	2.241	✓		RLM 3" 04	
	2.180	+0.005/-0.000	2.180	✓		↓	
	2.180	+0.005/-0.000	2.180	✓		↓	
	2.237	+0.005/-0.000	2.236		✓	↓	DUE TO VIBRATION
	2.272	+0.005/-0.000	2.270		✓	↓	
	2.306	+0.005/-0.000	2.307			↓	
	2.339	+0.007/-0.000	2.341	✓		VERNO 08	
	2.339	+0.007/-0.000	2.344	✓		"	
	0.062	+/-0.010	.0625	✓		RG	
	5.25	+/-0.060	5.284	✓		VERNO 08	
	R0.063	+/-0.010	.063	✓		RG	
	R0.50	+/-0.030	.5	✓		RG	
SIDE B	2.240	+/-0.005	2.238	✓		RLM 3" 04	
	2.180	+0.005/-0.000	2.178	✓		↓	
	2.180	+0.005/-0.000	2.178	✓		↓	
	2.237	+0.005/-0.000	2.2355	✓	✓	↓	DUE TO VIBRATION
	2.272	+0.005/-0.000	2.271	✓	✓	↓	
	2.306	+0.005/-0.000	2.306	✓	✓	↓	
	2.339	+0.007/-0.000	2.3415	✓		VERNO 08	
	2.339	+0.007/-0.000	2.3435	✓		"	
	0.062	+/-0.010	.0625	✓		RG	
	5.25	+/-0.060	5.258	✓		VERNO 08	
	R0.063	+/-0.010	.063	✓		RG	
	R0.50	+/-0.030	.5	✓		RG	
	112.27	+/-0.060	112.27	✓		TAPE	

DART AEROSPACE LTD		Work Order: 174690
Description: Crosstube Assembly (AS350/355 High Fwd)		Part Number: D350-748-141
Inspection Dwg: D350-748-141 Rev: H		Page 2 of 2

WALL THICKNESS MEASUREMENT

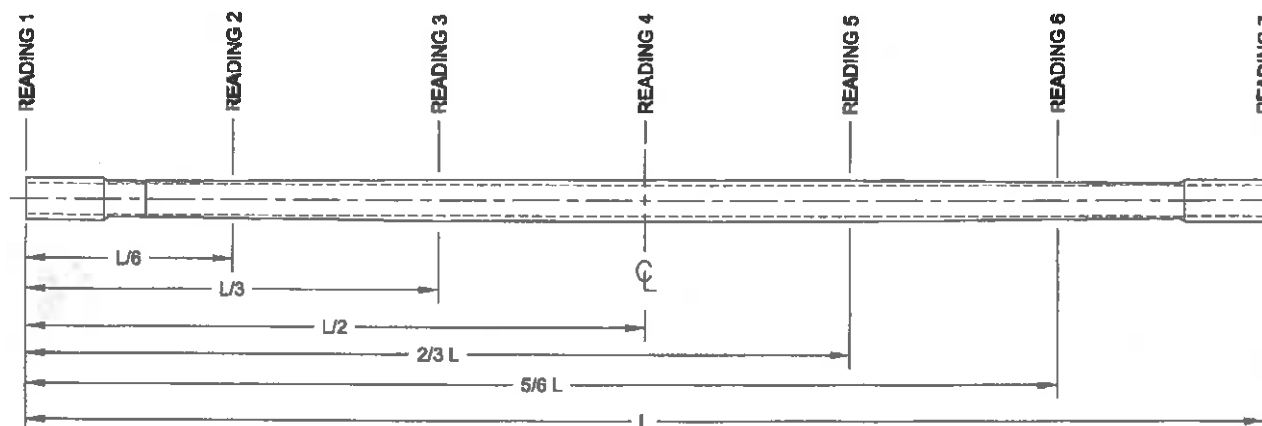

Location	WALL THICKNESS MEASUREMENT (IN)				Deviation Δw (max-min)	TOLERANCE
	w1	w2	w3	w4		
READING 1 L= 0"	.120	.116	.121	.118	.005	0.030"
READING 2 L= 18.71	.124	.123	.121	.120	.004	
READING 3 L= 37.42	.175	.165	.163	.171	.012	
READING 4 L= 56.14	.164	.164	.169	.168	.005	
READING 5 L= 74.85	.168	.168	.168	.167	.001	
READING 6 L= 93.56	.126	.120	.115	.120	.011	
READING 7 L= 112.27	.121	.116	.117	.121	.005	

Calibration Result

Actual Block Thickness: 100-200

Sitescan 250 Measured Thickness: 100 -200

Measured by: M.D	Audited by: JTW	Preliminary Approval:
Date: 2018-05-07	Date: 18-05-11	Date:

Rev	Date	Change	Revised by	Approved
D	11.07.26	Tolerance revised for 2.339 dimensions (P/O D350-748-101)	KJ	
E	12.06.04	Wall thickness form added	KJ	
F	13.05.08	Dimension 112.27 was 110.27	KJ	
G	14.04.25	5.25 dimension revised to 5.25	KJ	
H	15.04.14	Dwg Rev updated	KJ	
I	15.09.09	Tolerance updated for dimension 2.240	KJ	

Item	Qty	Part Number	Description
	-141		
1	X	D350-748-141	CROSSTUBE ASSEMBLY (AS 350/355 HI FWD)
2	1	D8015-125	CROSSTUBE (OR D8017-115)
3	2	D3502-1	SUPPORT
4	2	D6123-7	CLAMP CUSHION
5	1	AELS-1032-225	INSERT
6	1	NAS1149D0383J	WASHER (OR AN880JD10)
7	2	MS21920-20	CLAMP (OR MS21920-21/-22, PER DART SPEC. M-MS21920-20/-21/-22)
8	1	MS27038-1-10	SCREW
9	AR	PROSEAL 890 B-2	SEALANT, AMS-S-8802 CLASS B-2

GENERAL NOTES:


- 1) MATERIAL: MANUFACTURED FROM D8015-125 OR D8017-115
FINISHED LENGTH AFTER TURNING = 112.270±0.06 (AFTER BENDING/TRIMMING = 110.27 REF)
- 2) FINISH: MAGNETIC PARTICLE INSPECT PER DART QSI 038 4.2
MAGNETIC PLATE PER AMS-QQP-4168, CLASS 1, TYPE II
PRIME INSIDE AND OUTSIDE PER DART QSI 005 4.2
PAINT OUTSIDE PER DART QSI 005 4.2
- 3) TOLERANCE: PER DART QSI 016 UNLESS OTHERWISE NOTED.
WALL THICKNESS ECCENTRICITY PER DART QSI 038 7.2
MIN. ALLOWABLE WALL IS -0.020 FROM NOMINAL
PART IS SYMMETRIC ABOUT CENTERLINE, EXCEPT FOR Ø0.297 HOLE.
- 4) UNITS: INCHES UNLESS OTHERWISE NOTED.
- 5) BREAK SHARP EDGES: 0.005 TO 0.010 MAX.
- 6) IDENTIFICATION: PER DART NUMBER "D350-748-141" AND BATCH NUMBER ON INSIDE OF CUFF
PER DART QSI 044 & 4 (VIBRATING STYLUS)
- 7) WEIGHT: 30.45 lbs
- 8) PART IS SYMMETRIC ABOUT CENTERLINE, EXCEPT FOR Ø0.297 HOLE.
- 9) EXTREME CARE MUST BE TAKEN TO PROTECT THE OUTSIDE SURFACE OF THE TUBE. THE OUTSIDE SURFACE MUST BE SMOOTH AND FREE FROM SURFACE DEFECTS SUCH AS SCRATCHES, NICKS, OR DENTS. DEFECTS UP TO 0.005" MAY BE BLENDED OUT LONGITUDINALLY. CIRCUMFERENTIAL GRIND MARKS ARE UNACCEPTABLE. WHEN DRILLING HOLES EXTREME CARE MUST BE TAKEN AND CAREFUL DEBURRING PERFORMED TO ENSURE A CLEAN HOLE WITH NO CRACKING/CHIPPING/GROOVES.
- 10) BLEND OUT ALL EDGES FROM MACHINING LONGITUDINALLY. TRANSITION SHOULD BE SMOOTH. NOTE: ALL HOLES ARE DRILLED AFTER BENDING.
- 11) HEAT TREAT TO MIN. 180 KSI. PER MIL-T-5738 OR AMS2759/1E AFTER TURNING. ACCEPTABLE TO VERIFY TENSILE STRENGTH BY HARDNESS TEST PER ASTM E18 TO 40-45 HRC.
- 12) ALL DIMENSIONS FOR BENT TUBE ARE POST STRESS RELIEF
- 13) BEND PROGRESSIVELY WITH A MINIMUM OF 7 PASSES PER SIDE. MAXIMUM TUBE FLATTENING DUE TO BENDING IS 6% BASED ON O.D. ON TOP HALF OF BEND, AND 8% ON BOTTOM HALF OF BEND.
- 14) MAX AMPLITUDE OF RIBBLING ALONG BENT PORTION OF THE TUBE IS 0.030 (ZN A1-3)
- 15) AFTER BENDING, STRESS RELIEVE TUBE AT 650°F ±0.25°F FOR A MINIMUM OF 2 HRS AND ALLOW TO COOL TO AMBIENT TEMPERATURE (REF AMS2759/1E).
- 16) MAX TWIST AFTER STRESS RELIEF: WITH XTUBE LAYED FLAT ON SURFACE, THE DIFFERENCE BETWEEN CUFF HEIGHTS FROM THE SURFACE MAY BE NO LARGER THAN 0.38 (ZN C1-3).
- ASSEMBLY
- 17) TO INSTALL D3502-1 SUPPORT: ABRASE MATING SURFACE OF SUPPORT AND CROSSTUBE WITH 180-GRIT SANDPAPER AND REMOVE RESIDUE WITH MEK (OR EQUIVALENT). APPLY A 0.02" TO 0.05" THICK LAYER OF PROSEAL 890 CLASS B-2 (OR AMS-S-8802 CLASS B-2) SEALANT TO MATING SURFACE OF SUPPORT.
- 18) TORQUE CLAMPS 80 TO 90 IN-LB. ENSURE AT LEAST 1.5 THREADS SHOWING IN SAFETY AND THAT NUT HAS NOT BOTTOMED-OUT AFTER TORQUING. PRIOR TO PACKAGING, RE-CHECK TORQUE ON CLAMPS AFTER PROSEAL 890 SEALANT HAS CURED FOR 72 HOURS.

SHOP COPY
RETURN TO
ENGINEERING
UNCONTROLLED COPY
SUBJECT TO AMENDMENT
WITHOUT NOTICE
WORK ORDER
NO. 174690 MJS
180521


RELEASED
2015 MAR 18
9 EUN15-557

H	D8123-7 WAS D3586-083-383, MS21920-20 WAS -22, ALLOWABLE CRUSHING NOW 8% WAS 7%.	CP	15.02.25
G	RAY ABRASION STRIP, SUPPORT NOW W/ PROSEAL & CUSHION, ADD STRESS RELIEF, LONGER CUFF, NOW TRIMD AFTER BEND, ADD WALL DIMS & UPDATE TOL.	CP	12.06.12
F	ADD HRC TEST OPTION (B8-1) PER PAR 08-040, ADD TWIST LIMIT (A9-1, C1-3), ADD D8015-125 OPTION (C8-1), STOCK DIM NOW MACHINED (D1-4)	CP	10.11.23
E	REVISE GENERAL NOTES: UPDATE TO CURRENT ADD STANDARDS: RELOCATED FLAG #8 PER PAR 08-046 (ZN A8-3); TOLERANCES (ZN C8-3, D1-3)	RF	09.09.30
D	MAG. PARTICLE AND CAD PLATE AS MFD.	CP	08.10.31
C	ADD CAD PLATING	CP	08.08.14
B	ADD D8017-115 & PRIME AND PAINT	CP	08.08.30
A	NEW ISSUE	CP	08.03.31
REV.	DESIGN	BY	DATE
DESIGN			
DRAWN			
CHECKED			
MFG. APPR.			
APPROVED			
DE APPR.			
DATE	15.02.25		
DART AEROSPACE LTD HAWKESBURY, ONTARIO, CANADA			
REV. H DRAWING NO. D350-748-141 SHEET 1 OF 4			
TITLE CROSSTUBE (AS 350/355 HI FWD) SCALE NTS			
COPYRIGHT © 2005 BY DART AEROSPACE LTD THIS DOCUMENT IS THE PROPERTY OF DART AEROSPACE LTD. IT IS TO BE USED FOR THE PURPOSES FOR WHICH IT WAS ISSUED AND IS NOT TO BE REPRODUCED OR TRANSMITTED IN ANY FORM OR BY ANY MEANS, ELECTRONIC OR MECHANICAL, INCLUDING PHOTOCOPYING, RECORDING, OR BY ANY INFORMATION STORAGE AND RETRIEVAL SYSTEM, WITHOUT THE WRITTEN PERMISSION OF DART AEROSPACE LTD.			

17 18
D3502-1 SUPPORT
MS21820-20 CLAMP (OR -21/-22)
D5123-7 CLAMP CUSHION
2 PL

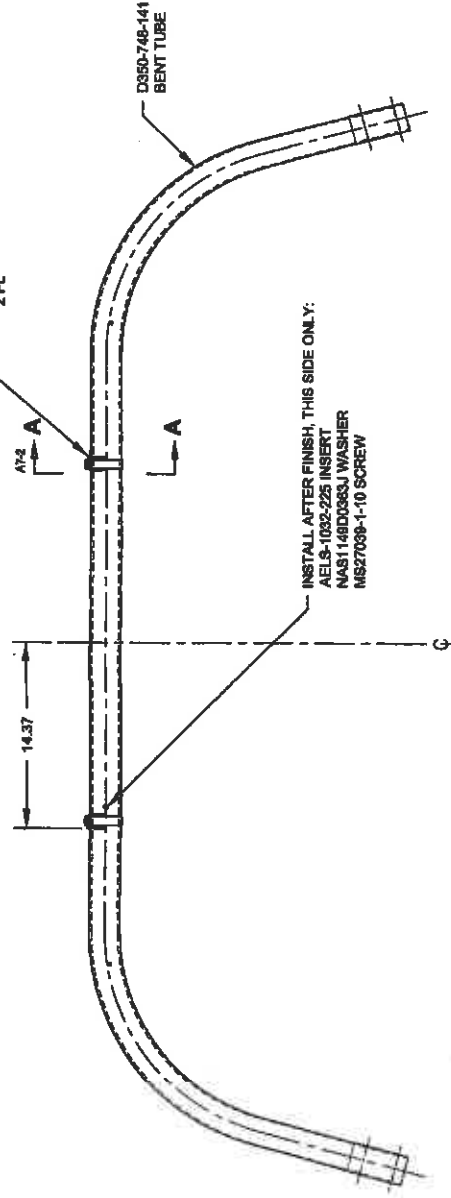


D350-748-141
ASSEMBLY DETAIL

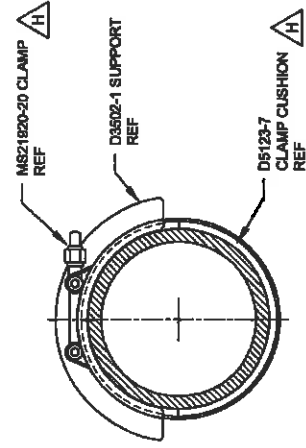

SECTION A-A 14-2
SCALE 6X

RELEASED
2015 MAR 18




DESIGN	00	DART AEROSPACE LTD HAWKESBURY, ONTARIO, CANADA
DRAWN	00	
CHECKED	ALS	DRAWING NO. D350-748-141
MPG. APPR.		REV. H SHEET 2 OF 4
APPROVED		TITLE
DE APPR.		CROSSTUBE (AS 350/355 HI FWD)
DATE	15.02.25	SCALE NTS
COPYRIGHT © 2008 BY DART AEROSPACE LTD THIS DOCUMENT IS UNCLASSIFIED AND IS NOT TO BE RELEASED TO THE PUBLIC WITHOUT THE WRITTEN PERMISSION OF DART AEROSPACE LTD		

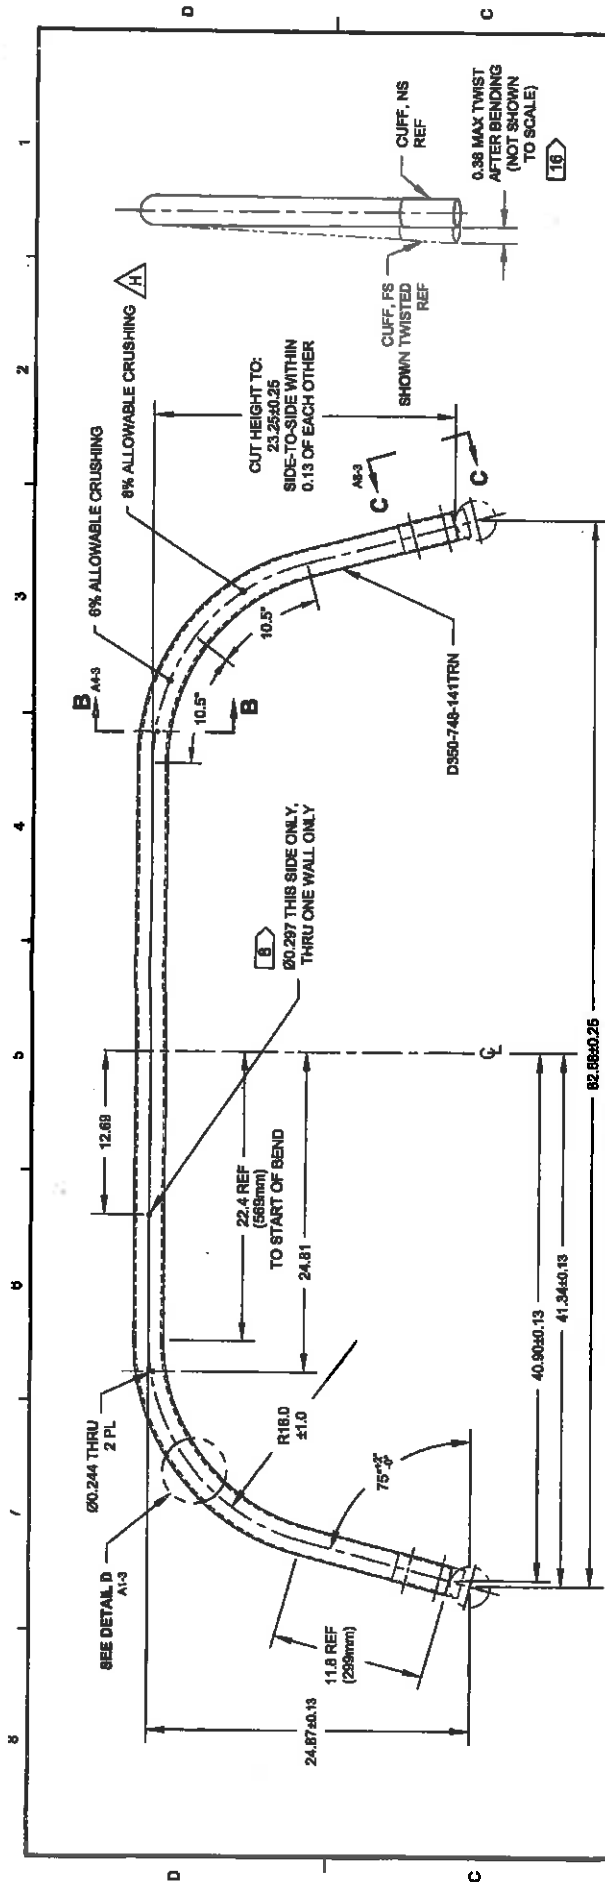

D350-748-141 **BENDING AND DRILLING DETAIL**


13

RELEASED
2015 MAR 18

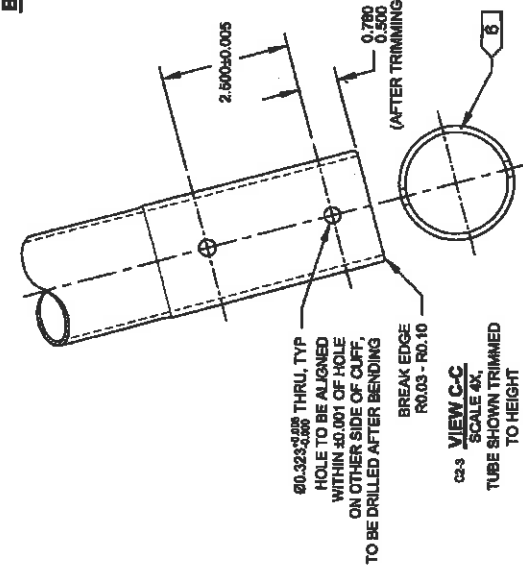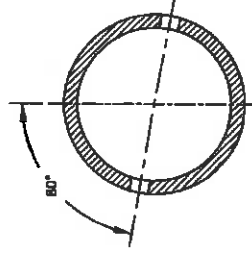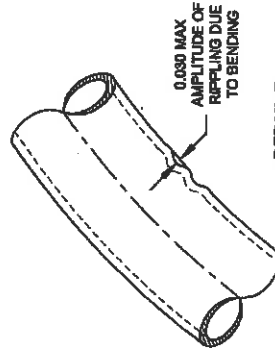

DESIGN	00	DART AEROSPACE LTD HARTFORD, ONTARIO, CANADA
DRAWN	00	
CHECKED	AS	DRAWING NO. D350-748-141
MFG. APPR.	AS	REV. H SHEET 3 OF 4
APPROVED	AS	TITLE CROSSTUBE (AS 350/355 HI FWD)
DE APPR.	AS	SCALE NTS
DATE	15.02.25	

COPYRIGHT © 2008 BY DART AEROSPACE LTD
THIS DRAWING IS THE PROPERTY OF DART AEROSPACE LTD
AND IS NOT TO BE REPRODUCED OR TRANSMITTED IN ANY FORM OR BY ANY MEANS, ELECTRONIC OR MECHANICAL, INCLUDING PHOTOCOPYING, RECORDING, OR BY ANY INFORMATION STORAGE AND RETRIEVAL SYSTEM, WITHOUT PERMISSION IN WRITING FROM DART AEROSPACE LTD.

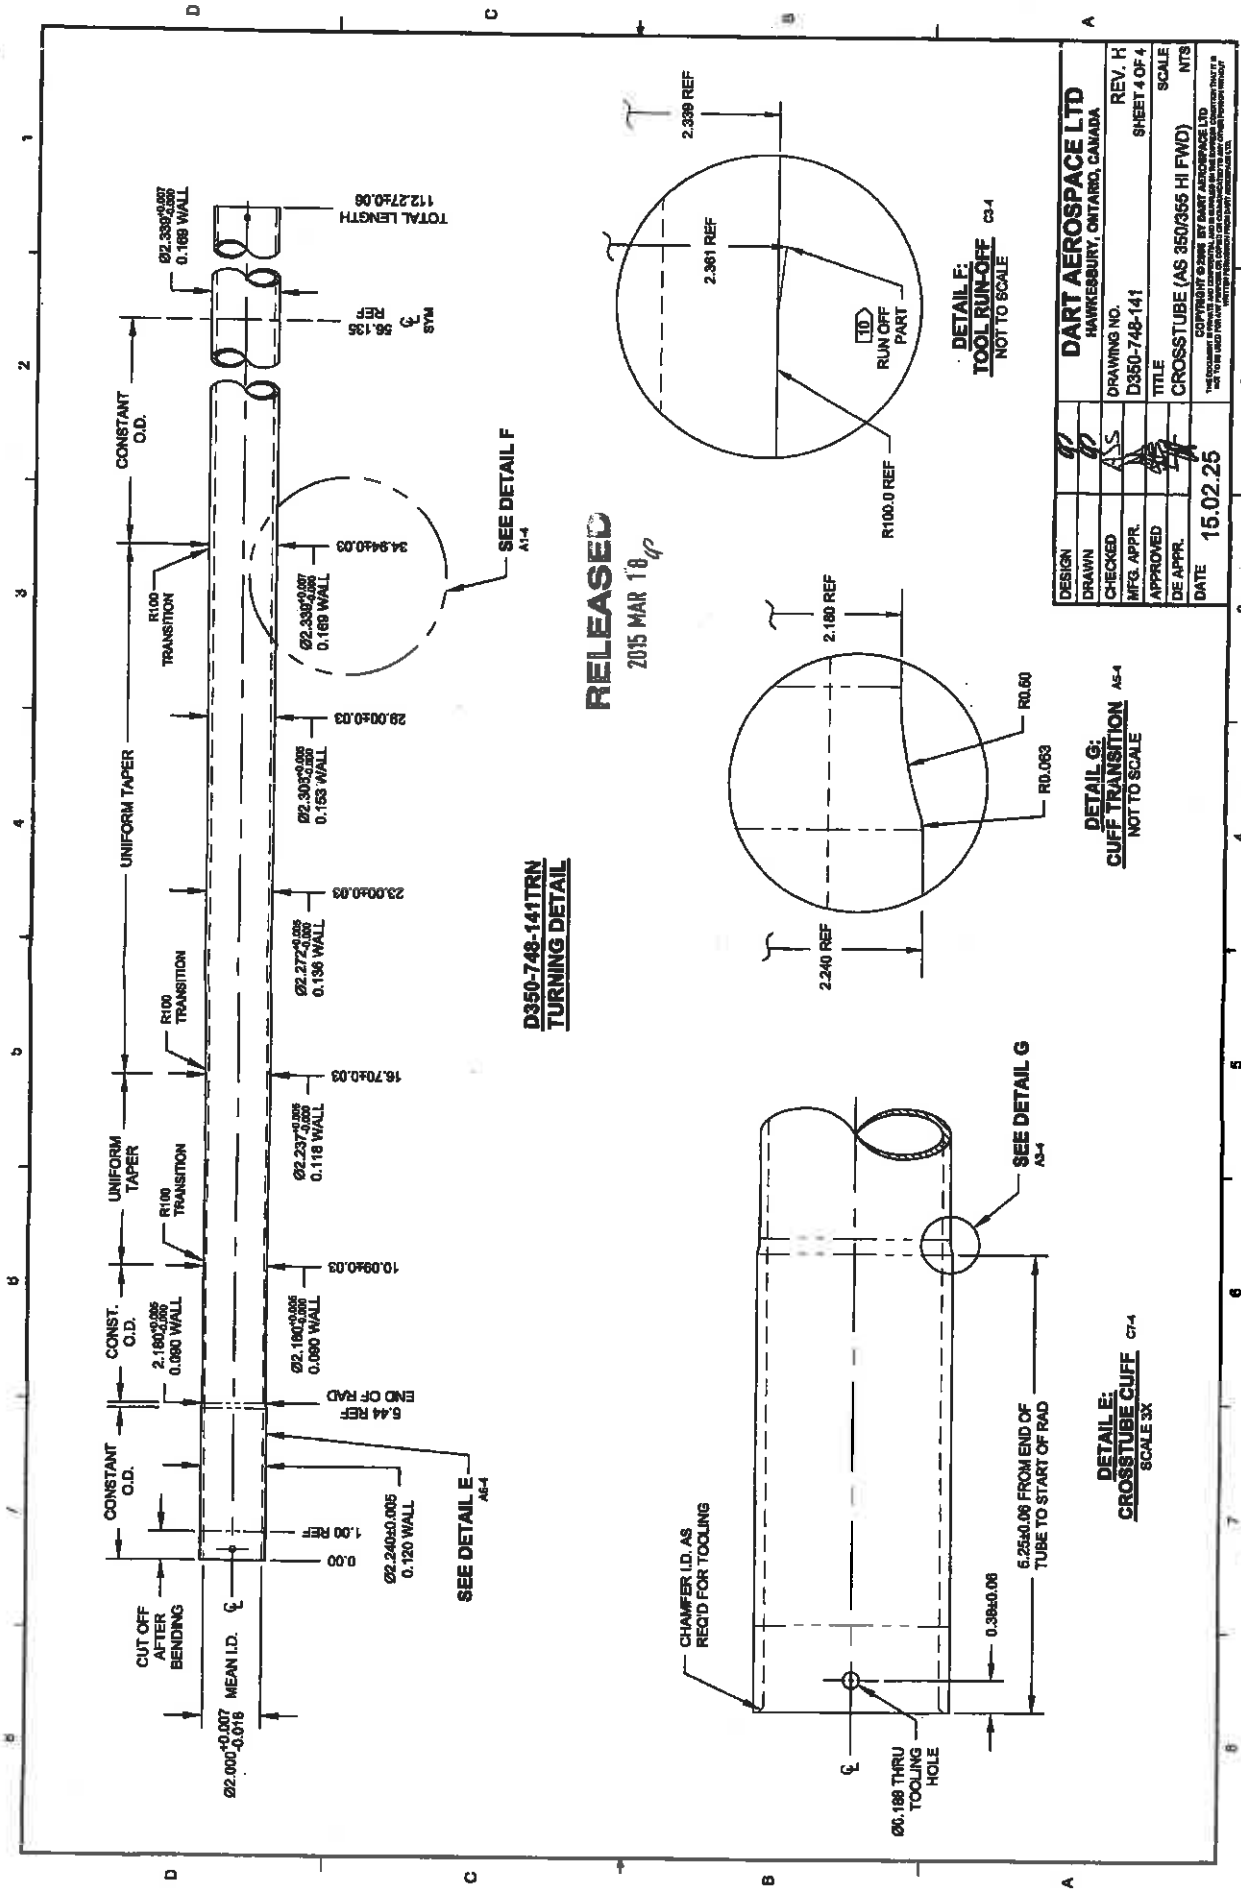

DESIGN	DART AEROSPACE LTD
DRAWN	HAWKESBURY, ONTARIO, CANADA
CHECKED	REV. H
INFO. APPR.	D350-748-141
APPROVED	SHEET 4 OF 4
DATE	15.02.25
TITLE	CROSS TUBE (AS 350/355 HI FWD)
SCALE	NTS

DETAIL G:
CUFF TRANSITION
NOT TO SCALE

DETAIL E:
CROSS TUBE CUFF
SCALE 3X

DETAIL E:
TOOL RUN-OFF
NOT TO SCALE



Dart Aerospace Ltd.
1270 Aberdeen St
Hawkesbury, ON
K6A 1K7
Canada

Tel (613) 632-5200

PURCHASE ORDER PO040105

Supplier: MET002-VU
Metlab
1000 E. Mermaid Lane
Wyndmoor, PA 19038 USA
Phone: 215-233-2600
Fax: 215-233-5653

PO No: PO040105
PO Date: 6/5/18
Due Date: 6/20/18
**Purchase Order
Revision:**
Revision Date:

Ship-To Contact: Phone:

Ship To: 1270 Aberdeen Street
Hawkesbury
ON
K6A 1K7 Canada
Phone: 613-632-5200

Via: Ground
Pymt Terms: Net 30

Freight Terms:

Special Comments:

Items

Line Item	Job	Part	Description	Status	Due Date	Order Quantity	Received Quantity	Balance	Unit Price (USD)	Extended Price
1	174757	D350-748- 241TRN	Crosstube Turning Detail Issue P/O: Heat Treat to min 180 KSI As per Dwg D350-748-241 ***Check for straighten and ensure parts are straight within 1/8" as per dwg *** Sand Blast tube after Heat Treat Possible Supplier: Vac Aero Ensure Certificate of Conformity is attached and Metlab process spec form	Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174761			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174756			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174751			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174754			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174752			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174763			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174750			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174759			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174764			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174765			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174762			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174758			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174755			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
	174760			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00
Sub Total:						15	0	15		\$3,075.00

PURCHASE ORDER

Items											
Item	Job	Part	Description	Status	Due Date	Order Quantity	Received Quantity	Balance	Unit Price (USD)	Extended Price	
2	174692	D350-748-141TRN	Crosstube Turning Detail Issue P/O: _____ Heat Treat to min 180 KSI As per Dwg D350-748-141 (MIL-T-6736 OR AMS 2759-1C) ***Check for straighten and ensure parts are straight within 1/8" as per dwg *** Sand Blast tube after Heat Treat Possible Supplier: Vac Aero Ensure Certificate of Conformity is attached and Metlab process spec form	Firmed	6/20/18	1 pcs	0 pcs 1k	1 pcs	\$205.00/pcs	\$205.00	
	174694			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174697			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174693			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174695			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174687			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174698			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174689			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174696			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174690			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174699			Firmed	6/20/18	1 pcs	1X 0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	177660			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174686			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174700			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00	
	174688			Firmed	6/20/18	1 pcs	0 pcs	1 pcs	\$205.00/pcs	\$205.00	
Sub Total:						15	0	15		\$3,075.00	

Grand Total: \$6,150.00

Order Notes

Procurement Quality Clauses
A005 right of entry
A012 chemical and physical test report
A016 personnel qualification
A017 raw material identification (as applicable)

A022 Apical Processing
A024 process certifications
A026 certification of material conformance

A041 quality management system
A042 dart notification by supplier
A043 retention of quality documents

A048 counterfeit parts avoidance, detection, mitigation and disposition program

A049 supplier awareness

Terms & Condition of Purchasing(Suppliers) and Procurement Quality Clauses are an integral part of our AS9100 requirements. To learn in detail, please visit www.dartaerospace.com for further explanation.

Plex 6/5/18 10:31 AM dart.tsimiklis.chrisoula

Certification - R

SOLD TO

Dart Aerospace
1270 Aberdeen St.
Hawkesbury, ON K6A 1K7
Canada


July 11, 2018

Metlab Shop Order:	100948
Purchase Order:	PO040105
Description:	Crosstube
Part Number:	D350-748-241TRN (15 Each) D350-748-141TRN (15 Each)
Weight:	1310 Pounds Total
Material:	4130 Alloy Steel
Specifications:	Harden and temper to 180 KSI minimum ultimate tensile strength (40 HRC surface hardness) per MIL-T-6736 or AMS 2759-1C. Maintain part straightness < 1/8" over total part length.

This is to certify that the above parts were processed as indicated above and conform to the specification requirements.

Results:

Hardness: 41/42 HRC

METLAB 
Quality Representative Matthew Robinson

MERCURY CONTAMINATION: During the heat treating process, testing and inspections, the product did not come in direct contact with mercury or any of its compounds nor with any mercury containing device.



Heat Treating and Metallurgical Consulting

METLAB
1000 E. MERMAID LANE
WYNDMOOR, PA 19038

Voice: 215-233-2600
Fax: 215-233-5653

Packing List

Sales Order Number:
100948

Sales Order Date:
Jun 7, 2018

Page:
1

Sold To:
DART AEROSPACE
1270 ABERDEEN STREET
HAWKESBURY, ON K6A 1K7
CANADA

Ship To:
DART AEROSPACE
1270 ABERDEEN STREET
HAWKESBURY, ON K6A 1K7
CANADA

Customer ID	PO Number	Payment Terms
DARA	PO040105	Net 30 Days
Ship Via	Process	
CALL CUSTOMER	HT	

Quantity	Item	Description	Total Shipped	This Shipment
30.00		30 PCS PART#: D350-748-241TRN CROSSTUBES HEAT TREAT TO MIN 180 KSI AS PER DWG D350-748-241 CHECK FOR STRAIGHTEN AND ENSURE PARTS ARE STRAIGHT WITHIN 1/8" AS PER DWG. SAND BLAST TUBE AFTER HEAT TREAT. 1310 POUNDS		
1.00	CERT.			

COMMENTS

SHIPPED BY, SIGNATURE DATE
METLAB

RECEIVED BY, SIGNATURE DATE
DART AEROSPACE